

# 17-7 PH STAINLESS STEEL

UNS S17700

- Good Formability
- High Strength
- Excellent Fatigue Properties
- Good Corrosion Resistance
- Minimum Distortion On Heat Treatment

## Applications Potential

AK Steel 17-7 PH® Stainless Steel provides valuable property combinations particularly well suited for aerospace applications. This special alloy also provides benefits for other applications requiring formability, high strength and good corrosion resistance, as well as excellent properties for flat springs, bellville washers, eyelets, and strain gauges at temperatures up to 600°F (316°C).

## Table of Contents

	Page
Applications Potential .....	1
Product Description .....	3
Composition .....	3
Available Forms .....	3
Metric Practice .....	3
Standard Heat Treatments .....	4
Mechanical Properties .....	5-8
Physical Properties .....	9
Corrosion Resistance .....	10-11
Formability .....	12
Weldability .....	12
Heat Treatment .....	12-13
Scale Removal .....	14
Specifications .....	15

The information and data in this product data bulletin are accurate to the best of our knowledge and belief, but are intended for general information only. Applications suggested for the materials are described only to help readers make their own evaluations and decisions, and are neither guarantees nor to be construed as express or implied warranties of suitability for these or other applications.

Data referring to mechanical properties and chemical analyses are the result of tests performed on specimens obtained from specific locations of the products in accordance with prescribed sampling procedures; any warranty thereof is limited to the values obtained at such locations and by such procedures. There is no warranty with respect to values of the materials at other locations.

AK Steel, the AK Steel logo, NITRONIC, 17-7 PH and PH 15-7 Mo are registered trademarks of AK Steel Corporation.

AK Steel 17-7 PH is a precipitation-hardening stainless steel that provides high strength and hardness, excellent fatigue properties, good corrosion resistance and minimum distortion upon heat treatment. It is easily formed in the annealed condition, then hardened to high strength levels by simple heat treatments to Conditions RH 950 and TH 1050. The exceptionally high strength of Condition CH 900 offers many advantages where limited ductility and workability are permissible.

In its heat-treated condition, this alloy provides exceptional mechanical properties at temperatures up to 900°F (482°C). Its corrosion resistance in both Conditions TH 1050 and RH 950 is superior to that of the hardenable chromium types. In some environments, corrosion resistance approximates that of the austenitic chromium-nickel stainless steels. In Condition CH 900, its general corrosion resistance is comparable to that of Types 302 and 304 stainless steels. Fabricating practices recommended for other chromium-nickel stainless steels can be used for this material.

### Composition

	%
Carbon	0.09 max.
Manganese	1.00 max.
Phosphorus	0.040 max.
Sulfur	0.030 max.
Silicon	1.00 max.
Chromium	16.00 - 18.00
Nickel	6.50 - 7.75
Aluminum	0.75 - 1.50

### Available Forms

AK Steel produces 17-7 PH Stainless Steel sheet and strip in thicknesses from 0.015" to 0.135" (0.381 to 3.429 mm). For material requirements heavier than 0.135" (3.429 mm), inquire. Material is supplied in Condition A, ready for fabrication by the user. Sheet and strip material 0.050" (1.27 mm) and thinner are also produced in the hard-rolled Condition C for applications requiring maximum strength.

### Metric Practice

The values shown in this bulletin were established in U.S. customary units. The metric equivalents of U.S. customary units shown may be approximate. Conversion to the metric system, known as the International System of Units (SI) has been accomplished in accordance with ASTM E380.

The newton (N) has been adopted by the SI as the metric standard unit of force. The term for force per unit of area (stress) is the newton per square meter (N/m<sup>2</sup>). Since this can be a large number, the prefix mega is used to indicate 1,000,000 units and the term meganewton per square meter (MN/m<sup>2</sup>) is used. The unit (N/m<sup>2</sup>) has been designated a pascal (Pa). The relationship between the U.S. and the SI units for stress is: 1000 pounds/in<sup>2</sup> = 1 kip/in<sup>2</sup> (ksi) = 6.8948 meganewtons/m<sup>2</sup> (MN/m<sup>2</sup>) = 6.8948 megapascals (MPa).


## Standard Heat Treatments

AK Steel 17-7 PH Stainless Steel requires three essential steps in heat treating:

- 1) Austenite conditioning.
- 2) Cooling to transform the austenite to martensite.
- 3) Precipitation hardening.

Table 1 presents the procedures for heat treating material in Condition A to Conditions TH 1050 and RH 950.

**Table 1**  
Standard Heat Treatments

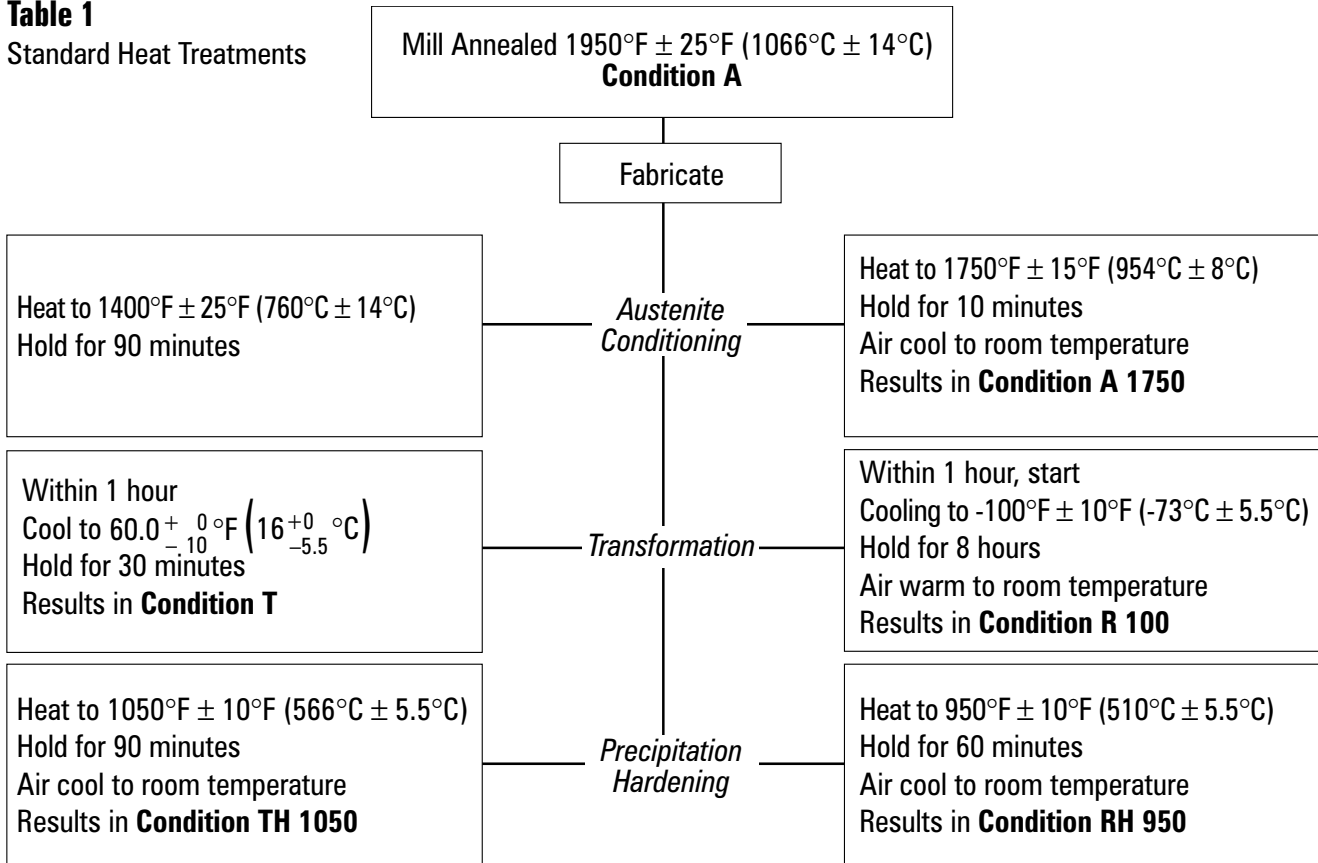


Note: Full strength may not be developed when cold worked material is heat treated to Condition TH 1050. However, full properties will be developed by using one of the following methods:

- 1) Re-anneal the fabricated part to Condition A and heat treat to Condition TH 1050.
  - 2) Heat treat fabricated part to an RH 1050 Condition.
  - 3) Use a modified TH 1050 heat treatment. For further information on this heat treatment, contact AK Steel or your distributor.
- No variation in properties is encountered when heat treating fabricated parts to Condition RH 950.

The highest mechanical properties obtainable from AK Steel 17-7 PH Stainless Steel are produced by Condition CH 900. To obtain these properties, Condition A material

is transformed to martensite at the mill by cold reduction to Condition C. Hardening to Condition CH 900 is accomplished with a single, low-temperature heat treatment.

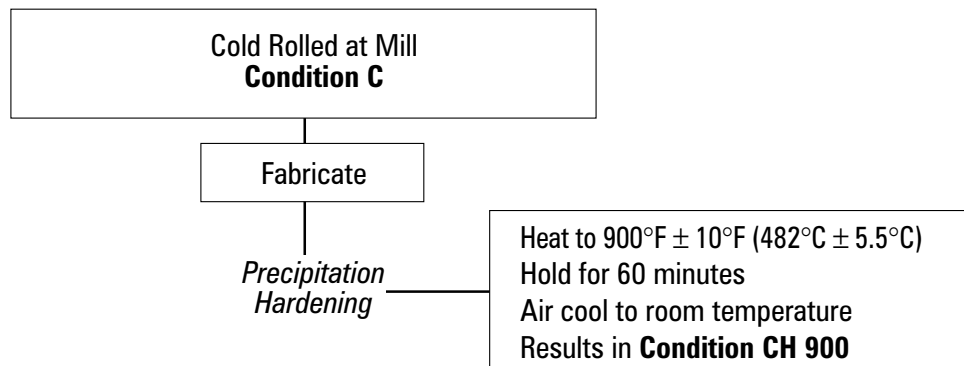

## Mechanical Properties

**Table 2**

Typical Room Temperature Mechanical Properties\*

Property	Condition							
	A	T	TH 1050	A 1750	R 100	RH 950	C	CH 900
UTS, ksi (MPa)	130 (896)	145 (1000)	200 (1379)	133 (917)	175 (1207)	235 (1620)	220 (1517)	265 (1827)
0.2% YS, ksi (MPa)	40 (276)	100 (690)	185 (1276)	42 (290)	115 (793)	220 (1517)	190 (1310)	260 (1793)
Elongation, % in 2" (50.8 mm)	35	9	9	19	9	6	5	2
Hardness, Rockwell	B85	C31	C43	B85	C36.5	C48	C43	C49

**Table 3**

Properties Acceptable for Material Specification\*

Property	Condition				
	A	TH 1050	RH 950	C	CH 900
UTS, ksi (MPa)	150 max. (1034)	180 min. (1241)	210 min. (1448)	200 min. (1379)	240 min. (1655)
0.2% YS, ksi (MPa)	55 max. (379)	150 min. (1034)	190 min. (1310)	175 min. (1207)	230 min. (1586)
Elongation, % in 2" (50.8 mm)	20 min.	—	—	1 min.	1 min.
0.036" - 0.1874" (0.91 - 4.7 mm)	—	6 min.	5 min.	—	—
0.020" - 0.0359" (0.50" - 0.89 mm)	—	6 min.	4 min.	—	—
0.010" - 0.0199" (0.25 - 0.49 mm)	—	5 min.	3 min.	—	—
Hardness, Rockwell**	B92 max.	C38 min.	C44 min.	C41 min.	C46 min.

\*Material 0.010" (2.54 mm) and thinner will have a maximum yield strength of 65 ksi (448 MPa).

\*\*Applies to material 0.010" (0.25 mm) and thicker. Selection of hardness scale is determined by material condition and thickness. Where necessary, superficial hardness readings are converted to Rockwell B or C.

**Table 4**

Fatigue Strength and Endurance Limit

Property	Condition			
	TH 1050	C	CH 900	RH 950
Endurance Limit (15 x 10 <sup>6</sup> cycles), ksi (MPa)				
Heat Treated Surface	63.5 (438)	–	–	77.5 (534)
Pickled Surface	62.5 (431)	–	–	–
Vapor Blasted Surface	82.1 (566)	–	–	100.0 (690)
Polished Surface (120 grit)	88.3 (609)	–	–	–
Fatigue Strength (10 <sup>7</sup> cycles), ksi (MPa)				
Heat Treated, Pickled or Polished Surface	–	–	82.3 (567)	–
0.2% Compressive Yield Strength, ksi (MPa)				
Transverse Direction	203 (1400)	218 (1503)	300 (2068)	240 (1655)

**Table 5**

Typical Elevated Temperature Short-Time Tensile Properties

Property	Temperature, °F (°C)						
	75 (24)	300 (149)	500 (260)	600 (316)	700 (371)	800 (427)	900 (482)
UTS, ksi (MPa)							
Condition TH 1050	193 (1331)	179 (1234)	167 (1151)	162 (1117)	156 (1076)	143 (986)	124 (855)
Condition RH 950	230 (1586)	208 (1434)	195 (1345)	189 (1303)	181 (1248)	160 (1103)	133 (917)
Condition CH 900	261.8 (1805)	248 (1710)	228 (1572)	222 (1531)	–	207 (1427)	182.4 (1258)
0.2% YS, ksi (MPa)							
Condition TH 1050	182 (1255)	170 (1172)	160 (1103)	155 (1069)	146 (1007)	130 (896)	100 (690)
Condition RH 950	217 (1496)	192 (1324)	176 (1213)	169 (1165)	162 (1117)	137 (945)	114 (786)
Condition CH 900	245.8 (1695)	233.5 (1610)	214 (1476)	203.5 (1403)	–	176.2 (1115)	143.5 (989)
Elongation, % in 2" (50.8 mm)							
Condition TH 1050	10.0	8.0	4.5	4.0	4.5	6.2	10.0
Condition RH 950	6.0	4.5	4.5	5.0	7.0	12.0	15.0
Condition CH 900	5.0	4.0	3.0	3.0	–	5.0	6.0

**Table 6**

## Stress to Rupture

Property	Temperature, °F (°C)			
	600 (316)	700 (371)	800 (427)	900 (482)
<b>In 100 Hours</b>				
Stress, ksi (MPa)				
Condition TH 1050	170 (1172)	130 (896)	110 (758)	78 (538)
Condition RH 950	188 (1296)	169 (1165)	113 (779)	61 (421)
Condition CH 900	220 (1517)	194 (1338)	135 (931)	53 (365)
<b>In 1000 Hours</b>				
Stress, ksi (MPa)				
Condition TH 1050	158 (1089)	122 (841)	90 (620)	52 (358)
Condition RH 950	180 (1241)	146 (1007)	92 (634)	44 (303)
Condition CH 900	216 (1489)	180 (1241)	73 (503)	36 (248)
<b>In 100 Hours</b>				
Elongation at rupture, % in 2" (50.8 mm)				
Condition TH 1050	19.0	21.0	21.0	30.0
Condition RH 950	13.0	21.0	15.0	33.0
Condition CH 900	10.0	11.0	20.0	14.0
<b>In 1000 Hours</b>				
Elongation at rupture, % in 2" (50.8 mm)				
Condition TH 1050	17.0	24.0	23.0	40.0
Condition RH 950	11.5	17.0	26.0	26.0
Condition CH 900	8.0	9.0	9.0	12.0

**Table 7**

## Creep Strength

Property	Temperature, °F (°C)			
	600 (316)	700 (371)	800 (427)	900 (482)
Stress in ksi (MPa) to produce:				
0.1% permanent deformation in 1000 hours				
Condition TH 1050	87.0 (600)	57.0 (393)	40.0 (276)	15.0 (103)
Condition RH 950	105.0 (724)	60.0 (414)	31.0 (214)	12.5 (86)
0.2% permanent deformation in 1000 hours				
Condition TH 1050	105.0 (724)	70.0 (483)	45.0 (310)	18.0 (124)
Condition RH 950	126.0 (869)	87.0 (600)	36.0 (248)	14.0 (96)



## Physical Properties

**Table 8**

	Condition A	Condition TH 1050	Condition RH 950	Condition CH 900
Density, lbs/in <sup>3</sup> (g/cm <sup>3</sup> )	0.282 (7.81)	0.276 (7.65)	0.276 (7.65)	0.277 (267)
Modulus of Elasticity, ksi (Gpa)	–	29.0 x 10 <sup>3</sup> (200)	29.0 x 10 <sup>3</sup> (200)	
Electrical Resistivity, microhm-cm	80	82	83	83.8
<b>Magnetic Permeability</b>				
@ 25 oersteds	1.4 - 3.4	132 - 194	82 - 88	–
@ 50 oersteds	1.4 - 3.6	120 - 167	113 - 130	–
@100 oersteds	1.4 - 3.5	80 - 99	75 - 87	70
@200 oersteds	1.4 - 3.2	46 - 55	44 - 52	43.5
Maximum	1.4 - 3.6	134 - 208	119 - 135	125
<b>Thermal Conductivity</b>				
BTU/hr/ft <sup>2</sup> /in/°F (W/m•K)				
300°F (149°C)	–	117 (16.87)	117 (est) (16.87)	114 (16.43)
500°F (260°C)	–	128 (18.46)	128 (est) (18.46)	127 (18.30)
840°F (449°C)	–	146 (21.05)	146 (est) (21.05)	150 (21.62)
900°F (482°C)	–	146 (21.05)	146 (est) (21.05)	151 (21.76)
<b>Mean Coefficient of Thermal Expansion in/in/°F (µm/m•K)</b>				
70 - 200°F (21- 93°C)	8.5 x 10 <sup>-6</sup> (15.3)	5.6 x 10 <sup>-6</sup> (10.1)	5.7 x 10 <sup>-6</sup> (10.3)	6.1 (11.0)
70 - 400°F (21-204°C)	9.0 x 10 <sup>-6</sup> (16.2)	6.1 x 10 <sup>-6</sup> (11.0)	6.6 x 10 <sup>-6</sup> (11.9)	6.2 (11.2)
70 - 600°F (21-316°C)	9.5 x 10 <sup>-6</sup> (17.1)	6.3 x 10 <sup>-6</sup> (11.3)	6.8 x 10 <sup>-6</sup> (12.2)	6.4 (11.5)
70 - 800°F (21-427°C)	9.6 x 10 <sup>-6</sup> (16.0)	6.6 x 10 <sup>-6</sup> (11.9)	6.9 x 10 <sup>-6</sup> (12.4)	6.6 (11.9)

Variations in heat-treating temperatures have negligible effect on electrical resistivity. Annealing, transforming and hardening treatment variations of  $\pm 100^\circ\text{F}$  ( $56^\circ\text{C}$ ) will not cause the resistivity to vary outside  $\pm 3\%$  from the listed value. Electrical resistivity value for Condition T is 107 microhm-cm.

No appreciable change in effective magnetic permeability exists in either Condition A or Condition TH 1050 between room temperature and  $500^\circ\text{F}$  ( $260^\circ\text{C}$ ).

### Dimensional Changes

When AK Steel 17-7 PH is heat treated from Condition A to either Condition RH 950 or TH 1050, a net dimensional expansion of approximately 0.004 inch per inch (mm/mm) occurs. This dimensional change is the result of first, an expansion of about 0.0045 inch per inch (mm/mm) resulting from the transformation treatment and a contraction of about 0.0005 inch per inch (mm/mm) resulting from the precipitation-hardening treatment.

Heat treating Condition C to Condition CH 900 results in a contraction of about 0.0005 inch per inch (mm/mm).

## Corrosion Resistance

Corrosion resistance of AK Steel 17-7 PH Stainless Steel in Conditions TH 1050 and RH 950 is generally superior to that of the standard hardenable chromium types of stainless steels such as Types 410, 420 and 431, but is not quite as good as chromium-nickel Type 304. Corrosion resistance in Condition CH 900 approaches that of Type 304 stainless steel in most environments.

### Atmospheric Exposure

Samples exposed at Kure Beach, North Carolina, show considerably better corrosion resistance to a marine atmosphere than hardened chromium stainless steels such as Type 410. Although there is little difference between any successive two ratings shown in Table 9, samples indicated the following order of corrosion resistance based on general appearance:

1. Type 301
2. 17-7 PH in Condition CH 900
3. 17-7 PH in Condition TH 1050
4. 17-7 PH in Condition RH 950

In all heat-treated conditions, the alloy, like other types of stainless steel, will develop superficial rust in some environments. For example, in a marine atmosphere, stainless steels show evidence of rusting after relatively short exposure periods. However, after exposure for one or two years, the amount of rust present is little more than that which was present at six months.

### Chemical Media

Hundreds of accelerated laboratory corrosion tests have been conducted on the precipitation-hardening stainless steels since their development. Table 9 shows typical corrosion rates for 17-7 PH and Type 304 stainless steels in seven common reagents. Sheet coupons and chemically pure laboratory reagents were used. Consequently, the data can be used only as a guide to comparative performance.

**Table 9**

Corrosion Rates in Various Media, mils per year\*

Corrosive Media	17-7 PH		Type 304
	TH 1050	RH 950	Annealed
<b>H<sub>2</sub>SO<sub>4</sub> – 95°F (35°C)</b>			
1%	0.5	0.2	0.4
2%	0.9	0.7	1.3
5%	124	132	7.7
<b>H<sub>2</sub>SO<sub>4</sub> – 76°F (80°C)</b>			
1%	50	297	22.2
2%	374	884 <sup>(2)</sup>	65
<b>HCl – 95°F (35°C)</b>			
0.5%	65	4	7.1
1%	695 <sup>(2)</sup>	447 <sup>(3)</sup>	17.3
<b>HNO<sub>3</sub> – Boiling</b>			
25%	19	20.4	1.2
50%	70	81	3.0
65%	128	136	7.2
<b>Formic Acid – 176°F (80°C)</b>			
5%	2.7	4.3	4.1
10%	5.5	5.7	18.0
<b>Acetic Acid – Boiling</b>			
33%	3.1	5.6	2.6
60%	12.3	3.0	10.9
<b>H<sub>3</sub>PO<sub>4</sub> – Boiling</b>			
20%	7.0	18	1.6
50%	24	46	8.5
70%	104	315	39
<b>NaOH – 176°F (80°C)</b>			
30%	13.1	3.7	0.9
<b>NaOH – Boiling</b>			
30%	67	58	17.5

\*Rates were determined by total immersion for five 48-hour periods. Specimens were activated during last three test periods in the 65% nitric acid. Rate is average of number of periods indicated in parentheses, if fewer than five periods were run.

### Corrosion Resistance and Compatibility in Rocket Fuels

**Oxygen** – While oxygen is highly reactive chemically, liquid oxygen is noncorrosive to most metals. The precipitation hardening stainless steels experience no problem in this medium.

**Ammonia** – AK Steel 17-7 PH is satisfactory for handling ammonia.

**Hydrogen** – Liquid hydrogen and gaseous hydrogen at low temperatures are noncorrosive.

### Stress Cracking in Marine Environments

The precipitation-hardening stainless steels, like the hardenable chromium stainless steels, may be subject to stress corrosion cracking when stressed and exposed to some corrosive environments. The tendency is related to the type of stainless steel, its hardness, the level of tensile stress and the environment.

AK Steel has conducted stress cracking tests on the precipitation-hardening alloys in the marine environment

at Kure Beach, North Carolina, using two-point loaded bent-beam specimens.

Data reported here are the results of multiple specimens exposed at stress levels of 50 and 75% of the actual yield strength of the materials tested. Test specimens were 0.050" (0.127 mm) thick heat treated to Conditions TH 1050 and RH 950. Specimens in Condition CH 900 were 0.041" (1.04 mm) thick. The long dimension of all specimens was cut transverse to the rolling direction.

When comparing the various heat-treated conditions, the data show that AK Steel 17-7 PH has the greatest resistance to stress cracking in Condition CH 900. Likewise, Condition TH 1050, although somewhat less resistant than Condition CH 900, appears to be more resistant to stress cracking than Condition RH 950.

Table 10 summarizes the test data. In addition, in the mild industrial atmosphere at Middletown, Ohio, specimens stressed at 90% of their yield strength had not broken after 730 days' exposure.

**Table 10**

Summary of Stress-Cracking Tests at Kure Beach\*  
(Average of 5 tests on each of 2 heats)

Heat Treatment	Stressed at 50% of the 0.2% YS			Stressed at 75% of the 0.2% YS		
	Stress ksi (MPa)	Days to Failure	Range Days	Stress ksi (MPa)	Days to Failure	Range Days
TH 1050	100.8 (694)	No failure in 746 days	–	151.3 (1043)	100 <sup>(2)*</sup>	82 - 118 <sup>**</sup>
TH 1050	89.0 (614)	No failure in 746 days	–	133.6 (921)	No failure in 746 days	–
RH 950	111.6 (769)	30.2	16-49	167.5 (1154)	7.4	6 - 10
RH 950	110.2 (759)	116 <sup>(1)*</sup>	–	165.4 (1141)	51.6	26 - 71
CH 900	142.8 (986)	No failure in 746 days	–	214.2 (1476)	No failure in 746 days	–

\*Number in bracket indicates number of failed specimens. Remainder of 5 specimens unbroken after 746 days.

\*\*Range of unbroken specimens only. Remainder of 5 specimens unbroken after 746 days.

NOTE: All tests made in transverse direction. Tests discontinued after 746 days' exposure.

## Formability

AK Steel 17-7 PH Stainless Steel in Condition A can be formed comparably to Type 301 stainless steel. It work hardens rapidly and may require intermediate annealing in deep drawing or in forming intricate parts. Springback is similar to that of Type 301.

This alloy is extremely hard and strong in Condition C. Therefore, fabrication techniques for such materials must be used.

## Weldability

The precipitation hardening class of stainless steels is generally considered to be weldable by the common fusion and resistance techniques. Special consideration is required to achieve optimum mechanical properties by considering the best heat-treated conditions in which to weld and which heat treatments should follow welding. This particular alloy is generally considered to have poorer weldability compared to the most common alloy of this stainless class, AK Steel 17-4 PH Stainless Steel. A major difference is the high Al content of this alloy, which degrades penetration and enhances weld slag formation during arc welding. Also, the austenite conditioning and precipitation hardening heat treatments are both required after welding to achieve high strength levels. When a weld filler is needed, W 17-7 PH is most often specified. More information can be obtained in the following way:

“Welding Stainless Steels,” FDB #SF-71.

## Heat Treatment

### Heat Treating and Annealing

For in-process annealing, the alloy should be heated to  $1950 \pm 25^\circ\text{F}$  ( $1066 \pm 14^\circ\text{C}$ ) for three minutes for each 0.1" (2.5 mm) of thickness, and air cooled. This treatment may be required to restore the ductility of cold-worked material so that it can take additional drawing or forming. Although most formed or drawn parts do not require re-annealing prior to hardening, annealing is required on severely formed or drawn parts to be heat treated to Condition TH 1050 if full response to heat treatment is required. Annealing is unnecessary in the case of the RH 950 heat treatment.

### Equipment and Atmosphere

Selection of heat-treating equipment depends to some extent on the nature of the particular parts to be treated. However, heat source, atmosphere and control of temperatures are the primary considerations.

Furnaces fired with oil or natural gas are difficult to use in the heat treatment of stainless steels, particularly if combustion control is uncertain and if flame impingement on the parts is possible. Electric furnaces, gas-and oil-fired radiant tube furnaces or vacuum furnaces generally are used for heat treating this material.

Air provides a satisfactory furnace atmosphere for heat-treating and annealing operations. Controlled reducing atmospheres such as dissociated ammonia or bright-annealing gas introduce the hazard of nitriding and/or carburizing or decarburizing and should *not* be used. Bright annealing may be accomplished in a dry hydrogen, argon, or helium atmosphere (dew point

approximately  $-65^{\circ}\text{F}$   $\{-54^{\circ}\text{C}\}$ ), if a cooling rate, approximately that obtained in an air cool can be used. Dry hydrogen, argon, or helium (dew point approximately  $-75^{\circ}\text{F}$   $\{-59^{\circ}\text{C}\}$ ) may be used for the  $1750^{\circ}\text{F}$  ( $954^{\circ}\text{C}$ ) heat treatment outlined for Condition RH 950, and will provide an essentially scale-free surface. At heat-treating temperatures of  $1400^{\circ}\text{F}$  ( $760^{\circ}\text{C}$ ) and lower, scale-free heat treatment in a dry hydrogen, argon, or helium atmosphere is difficult to achieve. A vacuum furnace is required for complete freedom from scale or heat discoloration.

Multiple exposures to a nitrogen atmosphere during annealing or quenching from vacuum may result in a surface layer of uniformly distributed small nitrides. These inclusions tend to decrease fabricability in subsequent cold-forming operations. Furnace loads should be such that cooling to  $1000^{\circ}\text{F}$  ( $538^{\circ}\text{C}$ ) may be effected within eight minutes to achieve best results.

It is necessary to cool this material to a temperature of  $-100^{\circ}\text{F}$  ( $-73^{\circ}\text{C}$ ) for a period of eight hours when heat treating to the RH condition. While commercial equipment is available for refrigeration at this temperature, a saturated bath of dry ice in alcohol or acetone maintains a temperature of  $-100$  to  $-109^{\circ}\text{F}$  ( $-73$  to  $-78^{\circ}\text{C}$ ) without control equipment.

Annealing at  $1950^{\circ}\text{F}$  ( $1066^{\circ}\text{C}$ ) or austenite conditioning at  $1750$  or  $1400^{\circ}\text{F}$  ( $954$  or  $760^{\circ}\text{C}$ ) in molten salts is not recommended because of the danger of carburization and/or intergranular penetration. However, hardening at  $900$  to  $1200^{\circ}\text{F}$  ( $482$  to  $649^{\circ}\text{C}$ ) has been done successfully with a few salts of the hydride or nitrate types.

### **Cleaning Prior to Annealing or Heat Treating**

Thorough cleaning of parts and assemblies prior to heat treatment greatly facilitates scale removal and is necessary for the development of uniform properties. Removal of oils and lubricants with solvents also assures that the steel will not be carburized from this source. Carburized 17-7 PH Stainless Steel will not respond properly to heat treatment.

Cleaning may be accomplished by the following two-step procedure:

1. Vapor degrease or solvent clean. This step removes oil, grease and drawing lubricants.
2. Mechanical scrubbing with mild abrasive cleaners, Oakite 33 or similar proprietary cleaners to remove dirt or other insoluble materials. All traces of cleaners should be removed by rinsing thoroughly with warm water.

A light, tightly adherent, uniform-appearing oxide after heat treatment is evidence of proper cleaning.

### **Coatings**

Protective coatings offer little advantage in reducing oxidation of the metal surface during heat treatments if the parts are thoroughly cleaned. However, when thorough cleaning is impractical, coatings may be beneficial. If such coatings are used, extreme caution must be exercised to provide free air circulation around the coated parts, or carburization may result.

## Scale Removal

Scale develops during most heat-treating operations. The amount and nature of the scale formation varies with the cleanliness of the parts, the furnace atmosphere and the temperature and time of heat treatment. A variety

of descaling methods may be employed, and the method chosen often depends upon the facilities available. A tabulation of the recommended scale removal methods after various heat treatments is shown in Table 11.

**Table 11**

### Scale Removal Methods

Heat Treated to Condition	Preferred Methods After Heat Treatment	Secondary Methods
A	Wet Grit Blast (1) or Pickle (2)	Scale Condition and Pickle (3)
CH 900	Wet Grit Blast (1) or Pickle (2)	– –
A 1750	Wet Grit Blast (1)	Pickle (2) or Scale Condition and Pickle (4)
T and R 100	Wet Grit Blast (1)	Pickle (2) or Scale Condition and Pickle (5)
TH 1050 and RH 950	Wet Grit Blast (1)	Pickle (2) or Scale Condition and Pickle (3)

- (1) Wet Grit Blasting processes are widely used and are highly satisfactory. These methods eliminate the hazard of intergranular attack from acid pickling. Added advantages are better fatigue strength and corrosion resistance.
- (2) 10% HNO<sub>3</sub> + 2% HF at 110 - 140°F (49 - 60°C) for three minutes maximum. Removal of loosened scale may be facilitated by the use of high-pressure water or steam spray. Scale-conditioning treatments are unnecessary for parts that have been thoroughly cleaned. Uniform pickling of the entire surface is evidence of a well-cleaned part. A spotty scale and non-uniform removal is evidence of a poorly cleaned part, and a scale conditioning process is necessary prior to pickling.
- (3) Scale conditioners:
  - (a) Hooker Electrochemical – Virgo Salts
  - (b) Kolene Process
  - (c) duPont Hydride Process
  - (d) Caustic permanganate (boiling 10% NaOH + 3% KMnO<sub>4</sub> for one hour)
- (4) Use caustic permanganate scale conditioning followed by HNO<sub>3</sub> – HF pickle only. Do not use fused salts. The use of fused salts on AK Steel 17-7 PH Stainless Steel in Condition A 1750 will prevent the steel from developing maximum transformation upon subsequent refrigeration.
- (5) Scale condition and pickle as in method 3. The Virgo and Kolene salt baths may be operated at temperatures up to 1100°F (593°C) so that the hardening and scale conditioning treatment may be combined if desired. However, the operation of a salt bath at such temperatures should be checked with the manufacturer before proceeding.

Some degree of intergranular penetration occurs during any pickling operation. However, the penetration from the short-time pickling of this material in Condition CH 900 is generally slight. Other conditions are more susceptible to intergranular penetration during pickling. Consequently, pickling should be avoided or carefully controlled if it must be used for such removal.

The standard 10% HNO<sub>3</sub> + 2% HF acid bath may be used for removal of light discoloration or heat tint produced by the final hardening treatment at 900 - 1200°F (482 - 649°C), providing immersion times are kept short (in the order of one minute or less).

## **Specifications**

The following specifications are listed without revision indications. Contact ASTM Headquarters, AMS Division of SAE or Department of Defense Index for latest revisions.

AMS 5528 Sheet, Strip and Plate

AMS 5529 Sheet and Strip – Cold Rolled

MIL-S-25043 Plate, Sheet and Strip

ASTM A 693 Plate, Sheet and Strip

(Listed as Grade 631- UNS S17700)



**Customer Service 800-331-5050**

**AK Steel Corporation**  
9227 Centre Pointe Drive  
West Chester, OH 45069

[www.aksteel.com](http://www.aksteel.com)

